

AD-A188 357

THE PREPARATION OF TITANIUM NITRIDE AND TITANIUM  
CARBONITRIDE BY THE PREC (U) MASSACHUSETTS INST OF  
TECH CAMBRIDGE DEPT OF CHEMISTRY D SEYFERTH ET AL

1/1


UNCLASSIFIED

04 NOV 87 N00014-82-K-0322

F/G 7/1

NL



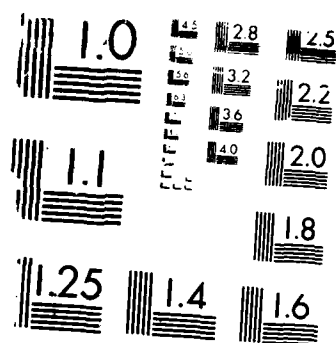

U.S. GOVERNMENT PRINTING OFFICE: 1963 O - 348-100

362

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

1a REPORT SECURITY CLASSIFICATION Unclassified			1b RESTRICTIVE MARKINGS	
2a SECURITY CLASSIFICATION AUTHORITY			3 DISTRIBUTION/AVAILABILITY OF REPORT Approved for public release. Distribution unlimited.	
2b DECLASSIFICATION/DOWNGRADING SCHEDULE				
4 PERFORMING ORGANIZATION REPORT NUMBER(S) 23			5 MONITORING ORGANIZATION REPORT NUMBER(S)	
6a NAME OF PERFORMING ORGANIZATION Massachusetts Institute of Technology		6b OFFICE SYMBOL (If applicable)		7a NAME OF MONITORING ORGANIZATION ONR
6c ADDRESS (City, State, and ZIP Code) Department of Chemistry 77 Massachusetts Avenue Cambridge, MA 02139			7b ADDRESS (City, State, and ZIP Code) Department of Navy Arlington, VA 22217	
8a NAME OF FUNDING/SPONSORING ORGANIZATION ONR		8b OFFICE SYMBOL (If applicable)		9 PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER
8c ADDRESS (City, State, and ZIP Code) Department of Navy Arlington, VA 22217			10 SOURCE OF FUNDING NUMBERS	
			PROGRAM ELEMENT NO N-00014-82	PROJECT NO K-0322
			TASK NO N631-618	WORK UNIT ACCESSION NO
11 TITLE (Include Security Classification) THE PREPARATION OF TITANIUM NITRIDE AND TITANIUM CARBONITRIDE BY THE PRECERAMIC POLYMER ROUTE				
12 PERSONAL AUTHOR(S) Dietmar Seyferth and Gerard Mignani				
13a TYPE OF REPORT Preprint		13b TIME COVERED FROM _____ TO _____		14 DATE OF REPORT (Year, Month, Day) 1987-11-4
15 PAGE COUNT				
16 SUPPLEMENTARY NOTATION Paper in J. Materials Science Letters				
17 DDC/ASI CODES			18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB-GROUP	titanium nitride titanium amides	
			titanium carbonitride ceramics	
19 ABSTRACT (Continue on reverse if necessary and identify by block number) The pyrolysis of selected titanium amides in a stream of ammonia gives titanium nitride. In a stream of argon titanium carbonitride is produced.				
20 DISTRIBUTION AVAILABILITY OF ABSTRACT <input checked="" type="checkbox"/> UNCLASSIFIED/NOTED <input type="checkbox"/> SAME AS RPT <input type="checkbox"/> OTHER			21 ABSTRACT SECURITY CLASSIFICATION Unclassified	
22a NAME OF RESPONSIBLE NO/LOCAL Dr. Seyferth, G. Mignani			22b FUNDING NUMBERS (Include Area Office) N631-618	

UNCLASSIFIED

SECURITY CLASSIFICATION OF THIS PAGE

## REPORT DOCUMENTATION PAGE

1a REPORT SECURITY CLASSIFICATION Unclassified		1b RESTRICTIVE MARKINGS	
2a SECURITY CLASSIFICATION AUTHORITY		3 DISTRIBUTION/AVAILABILITY OF REPORT Approved for public release. Distribution unlimited.	
2b DECLASSIFICATION/DOWNGRADING SCHEDULE			
4 PERFORMING ORGANIZATION REPORT NUMBER(S) 23		5 MONITORING ORGANIZATION REPORT NUMBER(S)	
6a NAME OF PERFORMING ORGANIZATION Massachusetts Institute of Technology	6b OFFICE SYMBOL (if applicable)	7a NAME OF MONITORING ORGANIZATION ONR	
6c ADDRESS (City, State, and ZIP Code) Department of Chemistry 77 Massachusetts Avenue Cambridge, MA 02139		7b ADDRESS (City, State, and ZIP Code) Department of Navy Arlington, VA 22217	
8a NAME OF FUNDING SPONSORING ORGANIZATION ONR	8b OFFICE SYMBOL (if applicable)	9 PROCUREMENT INSTRUMENT IDENTIFICATION NUMBER	
8c ADDRESS (City, State, and ZIP Code) Department of Navy Arlington, VA 22217		10 SOURCE OF FUNDING NUMBERS	
		PROGRAM ELEMENT NO N-00014-82	PROJECT NO K-0322
		TASK NO N631-618	WORK UNIT ACCESSION
11 TITLE (Include Security Classification) THE PREPARATION OF TITANIUM NITRIDE AND TITANIUM CARBONITRIDE BY THE PRECERAMIC POLYMER ROUTE			
12 PERSONAL AUTHOR(S) Dietmar Seyferth and Gerard Mignani			
13a TYPE OF REPORT Preprint	13b TIME COVERED FROM _____ TO _____	14 DATE OF REPORT (Year, Month, Day) 1987-11-4	15 PAGE COUNT
16 SUPPLEMENTARY NOTATION Paper in J. Materials Science Letters			
17 POSITIVE CODES		18 SUBJECT TERMS (Continue on reverse if necessary and identify by block number)	
FIELD	GROUP	SUB GROUP	
		titanium nitride	
		titanium carbide	
		titanium carbide	
19 ABSTRACT (Continue on reverse if necessary and identify by block number) A stream of air is selected titanium nitride in a stream of ammonia reacts titanium nitride in a stream of ammonia titanium carbide is produced.			
20 ABSTRACT AVAILABILITY STATEMENT UNCLASSIFIED		21 ABSTRACT SECURITY CLASSIFICATION UNCLASSIFIED	
22 NAME OF PERFORMING ORGANIZATION MASSACHUSETTS INSTITUTE OF TECHNOLOGY		23 ADDRESS (Include Area Code) 77 MASSACHUSETTS AVENUE CAMBRIDGE MA 02139	


# The Preparation of Titanium Nitride and Titanium Carbonitride by the Preceramic Polymer Route

Dietmar Seyferth\* and Gerard Mignani\*\*

Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, MA 02139 (USA)

Titanium nitride, TiN, is a very thermally stable (mp 2950°C) and a very hard (8 - 9 on the Moh scale) material. It is not attacked by acids (except hot aqua regia), but boiling alkalis decompose it. It is rapidly oxidized at high (~1200°C) temperatures by O<sub>2</sub>, NO and CO<sub>2</sub> [1]. The conventional routes for the preparation of titanium nitride all involve high temperature chemistry [1].

The thermal decomposition of simple mononuclear titanium amides has been reported as an alternate route to titanium nitride [2]. Eq. 1 gives one example. Also, the ammonolysis of [(CH<sub>3</sub>)<sub>2</sub>N]<sub>4</sub>Ti in liquid ammonia resulted in dimethylamine displacement and formation of a solid product of idealized formula Ti<sub>3</sub>(N)<sub>3</sub>(NH<sub>2</sub>)<sub>2</sub>[N(CH<sub>3</sub>)<sub>2</sub>] whose pyrolysis gave titanium nitride [3].

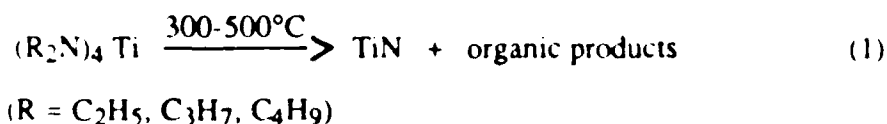


We have developed useful routes for the preparation of silicon [4] and boron [5] carbonitrides and nitrides by the pyrolysis of suitable polymeric precursors, and we were interested in developing such an approach for the synthesis of titanium carbonitride and nitride. We report some preliminary results.

The amine exchange reaction of [(CH<sub>3</sub>)<sub>2</sub>N]<sub>4</sub>Ti with various primary amines, RNH<sub>2</sub> (R = n-C<sub>4</sub>H<sub>9</sub>, n-C<sub>6</sub>H<sub>13</sub>, n-C<sub>8</sub>H<sub>17</sub>, CH<sub>3</sub>OCH<sub>2</sub>CH<sub>2</sub>) occurs in benzene solution at reflux, a reaction described by Bradley and Torrible in 1963 [6].

\* Author to whom inquiries should be addressed.

\*\* On leave from Rhône Poulenc Recherches, 1986.

With the unbranched primary amines the products are waxy red solids, average molecular weight greater than 1100, which are soluble in organic solvents. The IR and proton NMR spectra as well as the elemental analyses of these products could be rationalized in terms of Bradley's formulation of such materials as shown in formula I,

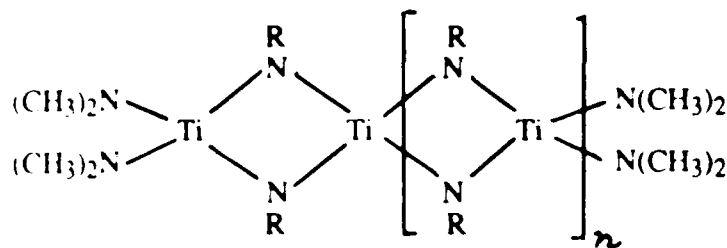


I

although the presence of some cyclic structures could not be excluded. Pyrolysis of the red solid obtained when *n*-butylamine was the primary amine used in a stream of dry ammonia (room temperature to 250°C at 10°C per min.; hold for 0.1 hr.; 250°C to 1000°C at 5°C per min., hold for 0.3 hr.) gave a golden-yellow solid residue (the color typical of TiN) in 32.3% (by weight) yield (calcd. for conversion of I, i.e., of  $[(C_4H_9N)_2Ti]_x$  to TiN: 32.6%). The analysis of the ceramic residue (76.7% Ti, 22.1% N, 0.26% C, 0.9% O, 0.08% H) was in fairly good agreement for that required for TiN (77.4% Ti, 22.6% N).

These results indicate that during the pyrolysis in a stream of ammonia an amine displacement reaction takes place, with amido (NH<sub>2</sub>) functions replacing C<sub>4</sub>H<sub>9</sub>N and terminal (CH<sub>3</sub>)<sub>2</sub>N substituents. At those temperatures and as the temperature is increased, thermal condensation processes then convert the intermediate titanium amides and imides to titanium nitride.

Similar reactions of  $[(CH_3)_2N]_4Ti$  with diamines were examined as well. Such reactions, carried out either in benzene solution at 80°C or with no solvent at 100–120°C using CH<sub>3</sub>NHCH<sub>2</sub>CH<sub>2</sub>NHCH<sub>3</sub>, C<sub>2</sub>H<sub>5</sub>NHCH<sub>2</sub>CH<sub>2</sub>NHC<sub>2</sub>H<sub>5</sub> and a commercial 85/15 mixture of CH<sub>3</sub>NHCH<sub>2</sub>CH<sub>2</sub>NHCH<sub>3</sub> and CH<sub>3</sub>NHCH<sub>2</sub>CH<sub>2</sub>NH<sub>2</sub> gave red, waxy solid products of low (225–350) average molecular weight (cryoscopy in benzene). A similar reaction with C<sub>2</sub>H<sub>5</sub>NH(CH<sub>2</sub>)<sub>3</sub>NHC<sub>2</sub>H<sub>5</sub> gave a red oil. Analyses of these products by fast atom bombardment mass spectrometry showed them to be a mixture of mainly the monotitanium species, II, but with also some higher oligomers, i.e., di, tri, etc. nuclear

species, present as well. All of these products were soluble in organic solvents. In contrast, such reactions of ethylenediamine itself did not give soluble products.

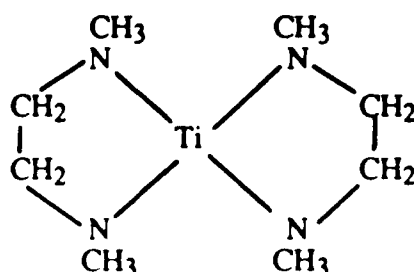

II

Pyrolysis of these titanium compounds derived from diamines under a stream of ammonia again gave fairly pure TiN. The example of the  $\text{CH}_3\text{NHCH}_2\text{CH}_2\text{NHCH}_3$  reaction product is typical. The red solid obtained in 61% yield (MW 234) in the reaction of 17.7 mmol of  $[(\text{CH}_3)_2\text{N}]_4\text{Ti}$  and 39.8 mmol of the diamine in 60 ml of benzene for 18 hr. at reflux was pyrolyzed in a stream of ammonia (temperature program as previously noted). A yellow ceramic residue was obtained in 26.7% yield (calcd TiN yield for this product, 28.1%). The analytical data (74.2% Ti, 23.5% N, 1.4% C, 0.5% O) indicated the formation of fairly pure TiN. A product of somewhat higher molecular weight (325) was obtained in a similar reaction of the 85/15  $\text{CH}_3\text{NHCH}_2\text{CH}_2\text{NHCH}_3/\text{CH}_3\text{NHCH}_2\text{CH}_2\text{NH}_2$  mixture with  $[(\text{CH}_3)_2\text{N}]_4\text{Ti}$  (MW for Ti species is 220; for the  $\text{Ti}_2$  species, 440). Pyrolysis to  $1000^\circ\text{C}$  under ammonia gave a yellow residue which contained 75.2% Ti, 22.5% N and only minor amounts of carbon and oxygen. Pyrolysis to  $1500^\circ\text{C}$  gave crystalline material whose powder X-ray diffraction lines matched those of authentic TiN.

When the pyrolysis of this precursor was carried out in a stream of argon to  $1000^\circ\text{C}$ , a black solid remained which contained 30.9% C in addition to Ti (45.5%) and N (9.9%). Obviously, a titanium carbonitride had been formed. The decomposition of the organonitrogen substituents provided carbon as well as nitrogen.

The approach which we describe is indeed a route to titanium nitride. The diamine-derived precursors at best are oligomeric, but the primary amine-derived materials are in the "preceramic polymer" molecular weight range and these merit further, more detailed investigation. A major drawback of these materials is the fact that their potential TiN content is quite low. For instance, in the case of the n-butylamine



product, 67.4% of the initial weight must be lost in the reaction with  $\text{NH}_3$  in order to obtain the theoretical amount of TiN. Ideally, on the basis of ceramic yield considerations, similar products with methyl- or ethylamine would be better, but these appear to be insoluble in organic solvents (hence not readily processable) although they may find some application in TiN synthesis.

Acknowledgements. The authors are grateful to the Office of Naval Research and to Rhône-Poulenc Recherches for generous support of this work.

## REFERENCES

1. J. Whitehead in "Kirk-Othmer Encyclopedia of Chemical Technology", Wiley, New York, Third Edition, vol. 23, pp. 135-136.
2. (a) K. Sugiyama, S. Pac, Y. Takahashi and S. Motojima, J. Electrochem. Soc., **122** (1975) 1545.  
 (b) V.V. Kutyreva, V.A. Varyukhin, O.N. Suvorova, B.A. Nesterov and G.A. Domrachev, Zh. Neorg. Khim., **15** (1979) 1692.  
 (c) L.M. Dyagileva, V.P. Marin, E.I. Tsyganova, I.L. Gaidym and Yu. A. Aleksandrov, Zh. Obshch. Khim. **54** (1984) 609.
3. G.M. Brown and L. Maya, Advanced Ceram. Mat., in press; see also L. Maya, in "Better Ceramics Through Chemistry II", C.J. Brinker, D.E. Clark and D.R. Ulrich, editors, Material Research Society: Pittsburgh, 1986, pp. 401-406.
4. (a) D. Seyferth and G.H. Wiseman, J. Am. Ceram. Soc., **66** (1983) C-13.  
 (b) D. Seyferth and G.H. Wiseman, J. Am. Ceram. Soc., **67** (1984) C-132.  
 (c) D. Seyferth and G.H. Wiseman, U.S. patent 4,482,669 (Nov. 13, 1984).
5. W.S. Rees, Jr. and D. Seyferth, J. Am. Ceram. Soc., in press.
6. D.C. Bradley and E.G. Torrible, Can. J. Chem. **41** (1963) 134.

DL/1113/87/2

TECHNICAL REPORT DISTRIBUTION LIST, GEN

	<u>No. Copies</u>		<u>No. Copies</u>
Office of Naval Research Attn: Code 1113 800 N. Quincy Street Arlington, Virginia 22217-5000	2	Dr. David Young Code 334 NORDA NSTL, Mississippi 39529	1
Dr. Bernard Douda Naval Weapons Support Center Code 50C Crane, Indiana 47522-5050	1	Naval Weapons Center Attn: Dr. Ron Atkins Chemistry Division China Lake, California 93555	1
Naval Civil Engineering Laboratory Attn: Dr. R. W. Drisko, Code L52 Port Hueneme, California 93401	1	Scientific Advisor Commandant of the Marine Corps Code RD-1 Washington, D.C. 20380	1
Defense Technical Information Center Building 5, Cameron Station Alexandria, Virginia 22314	12 high quality	U.S. Army Research Office Attn: CRD-AA-IP P.O. Box 12211 Research Triangle Park, NC 27709	1
DTNSRDC Attn: Dr. H. Singerman Applied Chemistry Division Annapolis, Maryland 21401	1	Mr. John Boyle Materials Branch Naval Ship Engineering Center Philadelphia, Pennsylvania 19112	1
Dr. William Tolles Superintendent Chemistry Division, Code 6100 Naval Research Laboratory Washington, D.C. 20375-5000	1	Naval Ocean Systems Center Attn: Dr. S. Yamamoto Marine Sciences Division San Diego, California 91232	1

ABSTRACTS DISTRIBUTION LIST, 356B

Professor T. Marks  
Department of Chemistry  
Northwestern University  
Evanston, Illinois 60201

Dr. Kurt Baum  
Fluorochem, Inc.  
680 S. Ayon Avenue  
Azusa, California 91702

Dr. Ulrich W. Suter  
Department of Chemical and Engineering  
Massachusetts Institute of Technologies  
Room E19-628  
Cambridge, MA 02139-4309

Dr. William Bailey  
Department of Chemistry  
University of Maryland  
College Park, Maryland 20742

Dr. J.C.H. Chien  
Department of Polymer Science and  
Engineering  
University of Massachusetts  
Amherst, MA 01003

Professor G. Whitesides  
Department of Chemistry  
Harvard University  
Cambridge, Massachusetts 02138

Dr. K. Paciorek  
Ultrasystems, Inc.  
P.O. Box 19605  
Irvine, California 92715

Dr. Ronald Archer  
Department of Chemistry  
University of Massachusetts  
Amherst, Massachusetts 01002

Professor D. Seyferth  
Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, Massachusetts 02139

Professor J. Moore  
Department of Chemistry  
Rensselaer Polytechnic Institute  
Troy, New York 12181

Dr. V. Percec  
Department of Macromolecular  
Science  
Case Western Reserve University  
Cleveland, Ohio 44106

Dr. Gregory Girolami  
Department of Chemistry  
University of Illinois  
Urbana-Champaign, IL 61801

Dr. Ted Walton  
Chemistry Division  
Code 6120  
Naval Research Lab  
Washington D.C. 20375-5000

Professor Warren T. Ford  
Department of Chemistry  
Oklahoma State University  
Stillwater, OK 74078

Professor H. K. Hall, Jr.  
Department of Chemistry  
The University of Arizona  
Tucson, Arizona 85721

Dr. Fred Wudl  
Department of Chemistry  
University of California  
Santa Barbara, CA 93106

Professor Kris Matjaszewski  
Department of Chemistry  
Carnegie-Mellon University  
4400 Fifth Avenue  
Pittsburgh, PA 15213

Professor Richard Schrock  
Department of Chemistry  
Massachusetts Institute of Technology  
Cambridge, MA 02139

ABSTRACTS DISTRIBUTION LIST, 356B

Professor A. G. MacDiarmid  
Department of Chemistry  
University of Pennsylvania  
Philadelphia, Pennsylvania 19174

Dr. E. Fischer, Code 2853  
Naval Ship Research and  
Development Center  
Annapolis, Maryland 21402

Professor H. Allcock  
Department of Chemistry  
Pennsylvania State University  
University Park, Pennsylvania 16802

Professor R. Lenz  
Department of Chemistry  
University of Massachusetts  
Amherst, Massachusetts 01002

Professor G. Wnek  
Department of Chemistry  
Rensselaer Polytechnic Institute  
Troy, NY 12181

Professor C. Allen  
Department of Chemistry  
University of Vermont  
Burlington, Vermont 05401

Dr. Ivan Caplan  
DTNSRDC  
Code 0125  
Annapolis, MD 21401

Dr. R. Miller  
Almaden Research Center  
650 Harry Road K91B801  
San Jose, CA 95120

Dr. William B. Moniz  
Chemistry Division  
Naval Research Laboratory  
Washington, D.C. 20375-5000

Dr. Richard M. Laine  
SRI International  
333 Ravenswood Avenue  
Menlo Park, California 94025

Dr. L. Buckley  
Naval Air Development Center  
Code 6063  
Warminster, Pennsylvania 18974

Dr. James McGrath  
Department of Chemistry  
Virginia Polytechnic Institute  
Blacksburg, Virginia 24061

Dr. Geoffrey Lindsay  
Chemistry Division  
Naval Weapons Center  
China Lake, California 93555

Professor J. Salamone  
Department of Chemistry  
University of Lowell  
Lowell, Massachusetts 01854

Dr. J. Griffith  
Naval Research Laboratory  
Chemistry Section, Code 6120  
Washington, D. C. 20375-5000

Professor T. Katz  
Department of Chemistry  
Columbia University  
New York, New York 10027

Dr. Christopher K. Ober  
Department of Materials Science  
and Engineering  
Cornell University  
Ithaca, New York 14853-1501

END

DATE

FILMD

3-88

DTIC